ISSN: 0254-8704
CODEN: JEBIDP

Volume 31 Number 3 May 2010

Journal of Environmental Biology

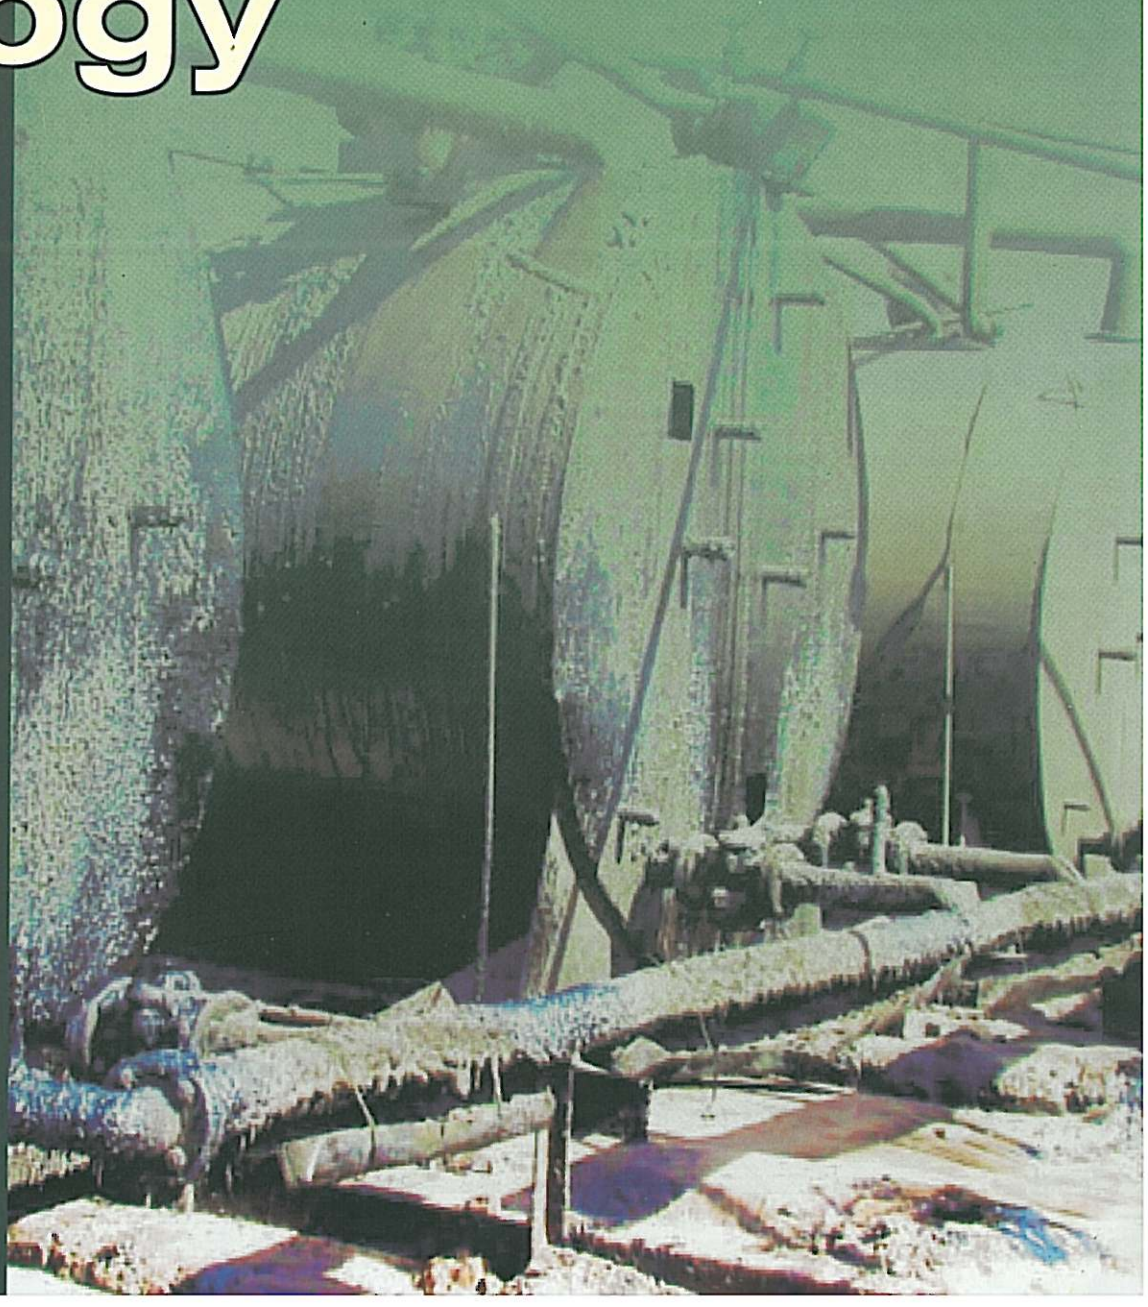

Founder
Editor-in-chief:
Dr. R.C. Dalela

Journal of Environmental Biology

Editorial Board - 2010

EDITOR-IN-CHIEF: Dr. R.C. DALELA, Environmentalist & Toxicologist, 1/206, Vikas Nagar, Lucknow-226 022 (India), editor@jeb.co.in
EXECUTIVE EDITOR: Dr. DIVAKAR DALELA, Professor, Department of Urology, C.S. Medical University, Lucknow-226 003 (India), drdalela@satyam.net.in

Research Editors

Dr. MUHAMMAD IQBAL, Hamdard Univ., New Delhi, India
Dr. S.V.S. RANA, Bundelkhand Univ., Jhansi, India
Dr. P. BALAKRISHNA MURTHY, IIBAT, Padappai, India
Dr. S.S.S. SARMA, UNAM Campus, Iztacala, Mexico
Dr. WILLIAM J. REA, EHC-Dallas, USA
Dr. S.J.S. FLORA, DRDE, Gwalior, India
Dr. GUY R. LANZA, Univ. of Massachusetts, USA
Dr. T.K. GHOSH, NEERI, Nagpur, India
Dr. MADHOOLIKA AGRAWAL, BHU,Varanasi, India
Dr. PIO COLEPICOLO NETO, Quimica Institute, USP, Brazil

Consulting Editors

Dr. C.N. SRIVASTAVA, DEI, Dayalbagh, India
Dr. S.V.S. CHAUHAN, ALS, Agra, India
Dr. J. MAHANTA, RMRC, Dibrugarh, India
Dr. JAYANTA K. DUTTA, B Univ., Burdwan, India
Dr. MARIANGELA ALBERTINI, Milano Univ., Italy
Dr. K.S. PILLAI, FTL, Chennai, India
Dr. MOHD. YUNUS, Univ. Putra, Malaysia
Dr. KRISHNA GOPAL, IITR, Lucknow, India
Dr. M.C. BHATNAGAR, Meerut College, Meerut, India
Dr. J.P. TRILLES, Montpellier Univ., France
Dr. R.C. RAY, CTCRI, Bhubneshwar, India
Dr. G. AGORAMOORTHY, Tajen Univ., Taiwan
Dr. KHAIWAL, Ravindra Univ. Hert Ford Shine. U.K.
Dr. XIN, CAS, P.R. China
Dr. QTAEJO, NFRDI, Korea
Dr. ANNA COSTA, Wyeth Lederle S.p.A., Italy
Dr. S. BARAT, NB Univ., Siliguri, India
Dr. A.K. KUMARAGURU, MK Univ., Madurai, India
Dr. S.K. BANSAL, DMRC, Jodhpur, India
Dr. SELCUK INAC, KS Univ., Turkey
Dr. M. SRIVASTAVA, NFREC Univ., Florida, USA
Dr. DIMITRA BOBORI, Aristotely Univ., Greece
Dr. H.C. SHARMA, ICRISAT, Patancheru, India
Dr. MALEEYA KRUATRACHUE, Mahidol Univ., Thailand

CONSULTANT (INFORMATION SYSTEMS): Mrs. ASMITA DALELA, 22 Rue Rousselle - 92800, Puteaux, Paris (France)
CONSULTANT (R & D): Dr. R.B. RAIZADA, Scientist (Retired), Indian Institute of Toxicology Research, M.G. Marg, Lucknow - 226 001 (India)

General Information

For Paper Submission: editor@jeb.co.in
For Subscription: info@jeb.co.in
For Paper Status: rnd@jeb.co.in
For Advertisement: editor@jeb.co.in

- **Copyright © 2010**
- All rights reserved throughout the world.
- No part of this publication should be reproduced in any form or by any means without prior permission in writing from the publishers.
- Responsibility regarding the authenticity of the data and the acceptability of the conclusions enforced/derived rests completely with the authors only.

Subscription Information for 2010

	For India	For Overseas
Annual Subscription	Rs. 2000.00	US$300.00
Single Copy	Rs. 300.00	US$60.00

- Send all payments in the form of Bank's Demand Draft in favor of "**Triveni Enterprises**" payable at **Lucknow (India)**.
- Journal is sent by registered post to subscriber.
- All payment should be made in advance.

Non-receipt of any issue of the Journal should be brought to the notice of Editor within two months of its release date. Copies lost in postal transit will be replaced only if available in stock.

Editorial Office

Journal of Environmental Biology, 1/206, Vikas Nagar, Lucknow - 226 022 (India)
e-mail: editor@jeb.co.in & info@jeb.co.in
Tel.: +91-522-2769181 (H), +91-522-4017359 (O); **Fax:** +91-522-2769018
Website: http://www.jeb.co.in

© Triveni Enterprises, Lucknow (India)
ISSN : 0254-8704
http : //www.jeb.co.in

Journal of Environmental Biology

Panel of Reviewers - 2010

CONSULTANT (R & D): Dr. R.B. RAIZADA, Scientist (Retired), Indian Institute of Toxicology Research, M.G. Marg, Lucknow - 226 001 (India)

For 31 (1&2 combined) 2010

Dr. Jinyang Deng
WVU, Morgantown, USA
Dr. Ramazan Ozcelik
SDU, Isparta, Turkey
Dr. Andrei Kandaurov
Institute of Zoology, Georgia
Dr. Nathalie Carisey
University Laval, Quebec, Canada
Dr. Murat Demir
Istanbul Univ., Bahcekoy, Turkey
Dr. Musa Genc
SDU, Isparta, Turkey
Dr. Ersin Yucel
ASU, Eskisehir, Turkey
Dr. Ahmet Aksoy
EU, Kayseri, Turkey
Dr. Farida Hanum
University of Putra, Malaysia

Dr. Dan Balteanu
UB, Romania
Dr. Abd Alla Gad
ESL, Cairo, Egypt
Dr. Tuncay Neyisci
AU, Antalya, Turkey
Dr. Parlas Konstantinidis
NFRI, Thessaloniki, Greece
Dr. Musa Aydogdu
GU, Ankara, Turkey
Dr. Georgia Ouzounidou
Nagref, Athens, Greece
Dr. Muhammad Ashraf
UA, Faislabad, Pakistan
Dr. Orhan Dengiz
QMU, Samsun, Turkey
Dr. S. Gokturk
AU, Antalya, Turkey

Dr. R. Bill
MU, Perth, WA, Australia
Dr. A. Tufekcioglu
CU, Artvin, Turkey
Dr. Aykut Guvensen
EU, Izmir, Turkey
Dr. Sedat Kadioglu
MEF, Ankara, Turkey
Dr. Ismail Belen
DEF, Gazi, Ankara, Turkey
Dr. Ergin Hamzaoglu
BU, Yozgat, Turkey
Dr. Gulcan S. Odabasi
OMU, Samsun, Turkey
Dr. Sinan Guner
CU, Artvin, Turkey
Dr. Erdogan Atmis
BU, Bartin, Turkey
Dr. Faruk A. Salamone
Iona College, NY, USA

For 31 (03) 2010

Dr. M. Balagopalan
KFRI, Peechi, Kerala
Dr. Xin Yu
IUE, CAS, Xiamen, China
Dr. K. Arun Kumar
Chennai, India
Dr. S.S.S. Sarma
UNAM, Mexico
Dr. P. K. Mishra
LU, Lucknow, India
Dr. Biswapati Mandal
BCKV, Kalyani, India
Dr. Nirmal De
BHU, Varanasi, India
Dr. Jayanta K. Datta
UB, Burdwan, India
Dr. T.K. Ghosh
NEERI, Nagpur, India
Dr. Mohd. Y.B.A. Shukor
UPM, Selangor, Malaysia

Dr. A.K. Saxena
NDUA&T, Faizabad, India
Dr. Guy R. Lanza
UM, Amherst, USA
Dr. P. Subramanian
BU, Tiruchirapalli, India
Dr. Basile Noitsakis
AUT, Greece
Dr. Emrah Cicek
DU, Duzce, Turkey
Dr. Sinan Guner
ACU, Artvin, Turkey
Dr. Upendra Nath Rai
NBRI, Lucknow, India
Dr. Muhammad Shafiq
UK, Karachi, Pakistan
Dr. Muthusamy A
BU, Tiruchirappalli, India
Dr. Johnny O. Ogunji
ESU, Abakaliki, Nigeria
Dr. Latif M. Jawad
U.B. Baghdad, Iraq

Dr. S. Barat
UNB, Siliguri, India
Dr. A.K. Kumaraguru
MKU, Madurai, India
Dr. Suleyman Korkut
DU, Duzce, Turkey
Dr. Anubha Kaushik
GJUST, Hissar, India
Dr. Mahmut Eroglu
KTU, Trabzon, Turkey
Dr. Ioannis Takos
TEIK, Greece
Dr. LALJI SINGH
IGKV, Raipur, India
Dr. Klaus von Gadow
Gottingen, Germany
Dr. Fahrettin Tilki
ACU, Artvin, Turkey
Dr. Ender Makineci
IU, Istanbul, Turkey

Abstracted / Indexed by

• Current contents (*Agriculture, Biology and Environ. Sci.*) • Current advances in ecological sciences (CAES) • Bio-science information service (BIOSIS) • Biological abstracts (BIOSIS Previews ®) • Environmental science database • Elsevier bibliographic databases • Cambridge science abstracts • Indian science abstracts • Forest science database • Environment complete™ • Environment abstracts • Paryavaran abstracts • Field crops abstracts • Toxicology abstracts • NISC SA databases • Chemical abstracts • Zoological records • CAB abstracts, U.K. • Pollution abstracts • Excerpta medica • Geoabstracts • Medline*

© Triveni Enterprises, Lucknow (India)
ISSN : 0254-8704
http : //www. jeb.co.in

J. Environ. Biol.
31, 351-355 (2010)
info@jeb.co.in

Some technological properties and uses of paulownia (*Paulownia tomentosa* Steud.) wood

M. Hakan Akyildiz*[1] and Hamiyet Sahin Kol[2]

[1]Kastamonu University, Faculty of Forestry, Department of Forest Industrial Engineering, 37100 Kastamonu, Turkey
[2]Karabuk University, Technical Education Faculty, Department of Furniture and Decoration Education, 78050 Karabuk, Turkey

(Received: January 23, 2009; Revised received: May 20, 2009; Accepted: July 25, 2009)

Abstract: *The aim of this study is to determine some physical and mechanical properties of Paulownia tomentosa wood grown in Turkey. The samples trees harvested from Kargi in Corum. Physical properties including air-dry density, oven-dry density, basic density, swelling, shrinkage and oven-dry and air-dry thermal conductivity coefficients; mechanical properties including bending strength, modulus of elasticity in bending, compression strength parallel to grain, hardness, bonding strength were analyzed. Paulownia tomentosa wood's air dry and oven dry densities were determined as 0.317 and 0.294 g cm^{-3}; basic density was determined as 0.272 g cm^{-3}; volumetric shrinkage and swelling were determined as 7.78 and 8.41%; tangential, radial and longitudinal air-dry thermal conductivity coefficients were determined as 0.089, 0.090 and 0.133 kcal/mh°C, respectively. Fiber saturation point (FSP) was found 28.79%; bending strength, Modulus of elasticity in bending, compression strength parallel to grain and Brinell hardness values (parallel and perpendicular to grain) were determined as 43.56 N mm^{-2}, 4281.32 N mm^{-2}, 25.55 N mm^{-2}, 2.01 kgf mm^{-2} and 0.88 kgf mm^{-2}, respectively. Consequently, paulownia wood can be widely used for various purposes such as house construction, furniture making, pulp and paper and handicrafts.*

Key words*: Paulownia tomentosa, Technological properties, Thermal conductivity*
PDF of full length paper is available online

Introduction

Paulownia is a deciduous tree capable of achieving very high growth rates under favorable conditions. *Paulownia tomentosa* Steud. is a fast growing tree species introduced in Turkey from China, where it is a widely spread species.

The genus *Paulownia* (Scrophulariaceae) includes nine species of fast-growing trees, indigenous to China and East Asia (Zhu *et al*., 1986). These trees were also introduced to North America, Australia, Europe and Japan. It could be considered as a low demand water plant, in spite of not growing in barren zones (Caparros *et al*., 2008). *Paulownia tomentosa* Steud. (Scrophulariaceae) is an ornamental tree widely distributed throughout China, Korea and Japan. Paulownia's characteristics of rot resistance, dimensional stability and a very high ignition point ensure the popularity of this timber in the world market (Bergmann, 1998; Silvestre *et al*., 2005).

Most species of paulownia are extremely fast growing and can be harvested in 15 years for valuable timber. Low quality lumber can easily be produced from 6-7 years old tree. A full grown paulownia can reach a height of 10 to 20 meters and grows up to 3 meters in one year under ideal conditions. A 10-year old tree can measure 30-40 cm diameter at breast height (DBH) and can have a timber volume of 0.3-0.5 m^3 (Flynn and Holder, 2001). Each paulownia tree could produce a cubic meter of wood at the age of 5–7 years; it may grow in intensive plantations with about 2000 trees per ha. Based on the above one can calculate that an annual production would be 330 ton ha^{-1}, a more conservative number would be about 150 ton ha^{-1} (Caparros *et al*., 2008).

The wood of paulownia is soft, lightweight, ring porous straight grained, and mostly knot free wood with a satiny luster. Average specific gravity of the wood is reported as 0.35 g cm^{-3} (Kalaycioglu *et al*., 2005; Flynn and Holder, 2001). Paulownia timber is easily air-dried without serious drying defects. It has a high strength-to-weight ratio, a low shrinkage coefficient, and does not easily warp or crack. Machining and finishing properties of the wood are excellent. In China and some of the other Asian countries, paulownia wood is used for a variety of applications such as furniture, construction, musical instrument, shipbuilding, aircraft, packing boxes, coffins, paper, plywood, cabinetmaking, and molding (Flynn and Holder, 2001; Clad and Pommer, 1980). Paulownia wood is marketed primarily for specialty solid wood products, oriented strand board, veneer, and for pulp to produce fine papers (Bergmann, 1998; Rai *et al*., 2000). Its stem bark has been used in Chinese herbal medicine as a component of remedies for infectious diseases such as gonorrhea and erysipelas (Kang *et al*., 1999; Asai *et al*., 2008). Aside from its continuing ornamental use, the species has value for its small sawn timbers that are in demand for specialty products. It is also used among Chinese folks to treat bronchitis, dysentery, bacterial dysentery, acute enteritis, parotitis and acute conjunctivitis, etc. (Liao *et al*., 2008). Some studies were done related to growth of Paulownia spp. in Turkey by Ulu *et al*. (2002) and Ayan *et al*. (2006) and similar studies going on.

* **Corresponding author:** akyildizmh@gmail.com

The main objective of this study is to determine some of the properties of *Paulownia tomentosa* wood, grown in Turkey as a fast growing species and to facilitate optimal utilization fields of this species.

Materials and Methods

For the present study, the sample tree of *Paulownia tomentosa,* 6 years-old and with a diameter at breast height diameter (DBH) of 30-40 cm tree, was harvested from Kargi the district of Corum on the north part of Turkey. The experimental area is located at an average altitude of 450 m. The tree of about 6.0-7.5 m high was cut into 0.5-2.0 m wood logs that were air-dried. Sections (1.5 m) were cut between 2 and 4 height of tree to obtain samples for the properties. The lumber was cut in parallel to grain directions from the logs in sawmill according to Turkish Standard (TS 4176, 1984). Afterwards cutting the lumbers were dried in uncontrolled air until at air dried moisture content about 12%.

Paulownia lumber was planed and then small clear specimens were cut for moisture content (MC), air-density (D_{12}) and oven-dry density (D_0) and basic density (D_b) and maximum moisture content (MMC) (20×20×30 mm), shrinkage (β) and swelling (α) (30×30×15 mm), oven-dry and air dry thermal conductivity coefficient (20×50×100 mm), compression strength parallel to grain ($\sigma_{c//}$) (20×20×30 mm), bending strength (σ_{sb}) and modulus of elasticity (MOE) in bending (20×20×320 mm), Brinell-hardness (H_B) (50×50×50 mm). Thermal conductivity measurements were performed based on ASTM C 1113-99 (ASTM, 2004) hot-wire method. The all other experiments were done according to Turkish Standards to determine densities (TS 2472, 1976), shrinkage (TS 4083, 1983) and swelling (TS 4084, 1983), compression strength parallel to grain (TS 2595, 1977), bending strength (TS 2474, 1976) and modulus of elasticity in bending (TS 2478, 1976), Brinell-hardness (TS 2479, 1976). Number of samples is used 30 samples in each test.

The wood samples were conditioned in a conditioning cabin at 20±2°C temperatures and 70±5% relative humidity to reach Equilibrium Moisture Content (EMC) throughout 8 weeks (TS 642, 1997). Afterwards conditioning, mechanical properties and thermal conductivity coefficients of Paulownia wood were determined. At the end of mechanical experiment, MC of all samples was measured according to TS 2471 (1976).

Quality values were calculated based upon a relationship between strength and density. Static (I_s) and specific (I_{sp}) quality values were calculated:

$$I_s = \sigma_{c//12} / D_{12} \times 100$$

$$I_{sp} = \sigma_{c//12} / (D_{12})^2 \times 100$$

where $\sigma_{c//12}$ is the compression strength parallel to grain in 12% MC (N mm^{-2}) and D_{12} is the air-dry (12%) density (g cm^{-3}) (Korkut and Guller, 2008; Bozkurt and Goker, 1987).

Basic density (D_b) was determined by using the following equation:

$$D_b = M_0 / V_g \ (g\ cm^{-3})$$

where M_0 is the oven-dry weight of the samples (g) and V_g is the green volume of the samples (cm^3).

Percentage of the cell wall (V_c) and percentage of the porosity (V_H) were also calculated by using the following equations:

$$V_c = D_0 / D_c \times 100 \ (\%)$$

$$V_H = 100 - V_c \ (\%)$$

where D_0 is oven dry density and D_c is oven dry density of the cell wall (1.5 g cm^{-3}).

Fiber saturation point (FSP) and maximum moisture content (MMC) were calculated by using the following equations:

$$FSP = \beta v / D_b \ (\%)$$

$$MMC = (1.5 - D_b) / (1.5 \times D_b) \ (\%)$$

where D_b is basic density and βv is the volumetric shrinkage (%).

Results and Discussion

Air-dry density (D_{12}), oven-dry density (D_0) and basic density (D_b) values were given Table 1. Arithmetic mean (X), maximum value (Max.), minimum value (Min.), standard deviation (SD), Variance (V), coefficient of variance (CV) were given for all properties.

Descriptive statistics for shrinkage (β) and swelling (α), fiber saturation point (FSP) and maximum moisture content (MMC) of *Paulownia tomentosa* were given Table 2.

The air-dry thermal conductivity coefficients were given in Table 3. According to the results, thermal conductivity in longitudinal direction was higher than those in the transverse direction. However, no significant difference was found between radial and tangential values.

Descriptive statistics for compression strength parallel to grain ($\sigma_{c//}$), bending strength (σ_{sb}), modulus of elasticity (MOE) in bending and Brinell-Hardness (H_B) of paulownia wood were given Table 4.

Percentage of the cell wall and percentage of porosity were calculated as 19.6% and 80.4% respectively.

Results were compared to values of paulownia ssp. grown in China. The results were also compared to some species of which have similar anatomical properties (Table 5).

Paulownia tomentosa grown in Turkey has quite low density because of fast growing and low percentage of cell wall. So, it has quite high percentage of porosity (80.4%). Decreasing

Table - 1: Basic statistics for air-dry density (D_{12}), oven-dry density (D_0) and basic density (D_b) (g cm^{-3})

Properties	Arithmetic mean (X)	Maximum value (Max.)	Minimum value (Min.)	Standard deviation (SD)	Variance (V)	Coefficient of Variation (CV)
D_{12}	0.317	0.357	0.263	0.021	0.0004	6.657
D_0	0.294	0.333	0.232	0.021	0.0005	7.269
D_b	0.272	0.311	0.226	0.018	0.0003	6.587

Table - 2: Basic statistics for shrinkage (β), swelling (α), fiber saturation point (FSP) and maximum moisture content (MMC) (%)

Properties	Arithmetic mean (X)	Maximum value (Max.)	Minimum value (Min.)	Standard deviation (SD)	Variance (V)	Coefficient of Variation (CV)
β –						
Radial	2.770	4.012	2.145	0.508	0.258	18.354
Tangential	5.013	6.369	3.238	0.803	0.645	16.019
Volumetric	7.783	9.004	6.679	0.528	0.279	6.786
α –						
Radial	2.480	3.518	2.014	0.409	0.167	16.481
Tangential	5.925	3.518	3.882	0.810	0.657	13.677
Volumetric	8.405	9.408	7.157	0.622	0.386	7.396
FSP	28.791	36.241	23.854	3.084	9.513	10.713
MMC	302.908	335.852	279.463	16.565	274.393	5.469

Table - 3: Basic statistics for thermal conductivity coefficients (kcal mh°C)

Properties	Arithmetic mean (X)	Maximum value (Max.)	Minimum value (Min.)	Standard deviation (SD)	Variance (V)	Coefficient of Variation (CV)
Tangential	0.089	0.095	0.077	0.0088	7.8E-5	9.89
Radial	0.090	0.101	0.081	0.0049	2.4E-5	5.44
Longitudinal	0.133	0.145	0.114	0.0122	1.5E-4	9.17

Table - 4: Basic statistics for compression strength ($\sigma_{c//}$), bending strength (σ_{sb}), modulus of elasticity (MOE), Brinell-hardness (H_B), static (I_s) and specific (I_{sp}) quality values

Properties	Arithmetic mean (X)	Maximum value (Max.)	Minimum value (Min.)	Standard deviation (SD)	Variance (V)	Coefficient of Variation (CV)
$\sigma_{c//}$ (N mm^{-2})	25.55	29.42	20.35	2.253	5.077	0.088
σ_{sb} (N mm^{-2})	43.56	60.37	33.36	7.006	49.080	0.161
MOE (N mm^{-2})	4281.32	5900.25	3338.30	783.366	613662.591	0.183
$H_B$kgf mm^{-2}						
Radial	0.84	0.99	0.73	0.094	0.009	0.112
Tangential	0.92	1.31	0.45	0.233	0.054	0.255
End-grain	2.01	2.92	1.53	0.374	0.140	0.186
I_s	8.10	10.31	6.93	0.818	0.669	0.101
I_{sp}	2.58	3.92	2.01	0.398	0.159	0.155

the ratio of cell wall increases the porosity, decreases the wood density. Consequently, maximum moisture content was found 302.9% which can be considered as a high value. Density closely correlates with physical, mechanical, hardness, transportation, heat value of wood, abrasion resistance, machining, electrical, acoustical and drying properties. Machining of high density wood is relatively difficult (Goker *et al*., 1999).

The density of paulownia was found 0.317 g cm^{-3}. So, paulownia can be called as light wood according to Bozkurt and Erdin's (1990). Lightness is a major advantage of paulownia wood (Anon., 1986). According to Table 5, *Paulownia tomentosa* grown in Turkey has the lowest density value among all of the species grown in Turkey. However, naturally grown paulownia species have almost same density value. Thus, it can be say that paulownia grown in Turkey have same physical and mechanical properties because most mechanical properties of wood are closely correlated to density (Anon., 1999). The existence of a strong relationship between wood density and strength has been demonstrated by several investigators (Kollmann and Cote, 1984; Pernestal *et al*., 1995; Hernandez, 2007).

Table - 5: Comparison of physical and mechanical properties of *Paulownia tomentosa* with other tree species

Species	D_{12} g cm^{-3}	D_0 g cm^{-3}	D_b g cm^{-3}	β_v %	α_v %	FSP %	$\sigma_{c///}$ N mm^{-2}	MOE N mm^{-2}	σ_{sb} N mm^{-2}	H_B kgf mm^{-2} //	H_B kgf mm^{-2} ⊥	Reference
Paulownia tomentosa	0.317	0.294	0.272	7.78	8.41	28.79	25.55	4281.32	43.56	2.01	0.88	
Paulownia tomentosa	0.315	0.236		9.24[a]			21.87	4707.19	39.82	1.83	1.26	Anonymous, 1986
Paulownia elongate	0.264	0.209		8.12[a]			15.59	4118.79	28.34	1.25	0.85	Anonymous, 1986
Paulownia fortunei	0.309	0.258		8.96[a]			18.44	6178.19	39.72	2.15	1.24	Anonymous, 1986
Populus tremula	0.450	0.420		12.8			39.23	7649.19	50.99	2.3	1.1	Bozkurt and Erdin, 1997
Alnus glutinosa	0.511	0.502	0.434	13.24	14.14	30.5	41.48 55.35*	8611.81	77.53 95.10*	2.89 3.06*	1.50 1.53*	*Ay, 1998; Ors and Ay, 1999;Guller and Ay, 2001
Castanea sativa	0.540	0.508	0.448	11.47		25.59	57.07		77.47	4.25	1.72	Ay and Sahin, 2002a Ay and Sahin, 2002b
Fagus orientalis L.	0.669	0.645	0.538	16.21	17.84	30.13	56.09	12829.3	110.13	5.49	2.75	Malkocoglu, 1994

[a] The values given as coefficient were converted to percentage

Table - 6: Comparison of thermal conductivity of *Paulownia tomentosa* with other tree species

Wood species	Density g cm^{-3}	Thermal conductivity (kcal mh^{-1}°C) Longitudinal	Radial	Tangential	Reference
Paulownia tomentosa	0.317	0,133	0,090	0,089	
Populus tremula	0,382	0,156	0,130	0,099	Ors and Senel, 1999
Fagus orientalis	0,687	0,261	0,171	0,145	

Volumetric shrinkage and swelling of paulownia wood were found lower than that of similar species. Radial, tangential and volumetric shrinkage of paulownia wood has been took place the class of low shrinkage wood (Bozkurt and Erdin, 1990). This property provides very important advantage in different use of field as furniture. Fiber saturation point was found 28.8% that is normal value for all species.

Thermal conductivity of *Paulownia tomentosa* grown in Turkey was found very low thus giving it excellent heat/cool insulation properties (Table 6). So, Paulownia can be used as a material in construction where the isolative is required.

The hardness of paulownia was also determined to be low value ($H_{B//}$ 2 kgf mm^{-2} and $H_{B\perp}$ 0.88 kgf mm^{-2}). So, paulownia wood can be classified as very low according to Bozkurt and Erdin's (1990) classification. In addition to this, the wood can be classified very soft wood according to hardness classification ($H_{B\perp}$) (Ors and Keskin, 2001). The pliable wood has low strength. Thus, it is not suitable for using as building components that usually require high strength (Anon., 1986).

However, the compression strength (25.55 N mm^{-2}) and bending strength (43.56 N mm^{-2}) values of paulownia were found higher than that grown in China. So, it is suitable for some uses requiring soft but relatively high strength wood. Modulus of elasticity of paulownia was found lower than that of compared species. The wood can be classified very low and low for compression strength, MOE and bending strength respectively according to Bozkurt and Erdin's (1990) classification.

Hardwoods can be classified as low (I_s<6), fair (6<I_s<7) and good (7<I_s) quality according to their static quality value (I_s). Limit values for the classification change depend on density and hardness of species (Kollmann and Cote, 1984). According to this classification, *Paulownia tomentosa* (I_s=8.10) has a good quality wood.

Paulownia wood is not suitable for uses which require mechanical strength, but it is widely used for houses as roof beams and purlin. Paulownia wood is light, rot-resistant and free of warping, cracks and knots, so, it can be used for model air-planes, aircrafts, gliders and building material for plywood chairs and tables. Due to increased delivery volume it can be used for packing boxes.

References

Anonymous: Paulownia in China: Cultivation and utilization. Asian Network for Biological Sciences. Chinese Academy of Forestry, Beijing-China. p. 65 (1986).

Anonymous: Wood handbook, forest products laboratory, US Department of Agriculture, MI, USA (1999).

Asai, T., N. Hara, S. Kobayashi, S. Kohshima and Y. Fujimoto: Geranylated uavanones from the secretion on the surface of the immature fruits of *Paulownia tomentosa*. *Phytochemistry*, **69**, 1234-1241 (2008).

ASTM C 1113-99: Standard test method for thermal conductivity of refractories by hot wire (Platinum Resistance Thermometer Technique). American Society for Testing and Materials-ASTM-International; West Conshohocken, USA (2004).

Ay, N.: Mechanical properties of Alder [*Alnus glutinosa* subsps. *barbata* (C.A. Mey.) Yalt.] wood obtained from Rize-Cayeli region. Pamukkale University. *J. Eng. Sci.*, **4**, 641-647 (1998).

Ay, N. and H. Sahin: Physical properties of Chestnut (*Castanea sativa* Mill.) wood obtained from Maçka-Çatak region. Kafkas University. *J. Artvin Forestry Faculty*, **1**, 63-71 (2002a).

Ay, N. and H. Sahin: Some mechanical properties of Chestnut (*Castanea sativa* Mill.) wood obtained from Macka-Catak region. Kafkas University. *J. Artvin Forestry Faculty*, **1**, 87-95 (2002b).

Ayan, S., A. Sivacioglu and N. Bilir: Growth variation of Paulownia Sieb. And Zucc. species and origins at the nursery stage in Kastamonu-Turkey. *J. Environ. Biol.*, **27**, 499-504 (2006).

Bergmann, B.A.: Propagation method influences first year field survival and growth of Paulownia. *New Forests*, **16**, 251-264 (1998).

Bozkurt, A.Y. and N. Erdin: Ticarette kullanilan agaclarda fiziksel ve mekanik ozellikler. Iu. Orman Fakultesi Dergisi. Seri:B., **40**, 6-24 (1990).

Bozkurt, A.Y. and N. Erdin: Wood material technology handbook. Istanbul University Publication No. 3998, Faculty of Forestry Publication No: 445. ISBN 975-404-449-X, Istanbul (1997).

Bozkurt, Y. and Y. Goker: Physical and mechanical wood technology, Istanbul University Publication No:3445. Faculty of Forestry Publication No:388, Istanbul (1987).

Caparros, S., M.J. Diaz, J. Ariza, F. Lopez and L. Jimenez: New perspectives for Paulownia fortunei L. valorisation of the autohydrolysis and pulping processes. *Bioresource Technol.*, **99**, 741-749 (2008).

Clad, W. and E. Pommer: Manufacture of particleboard from kiri (*Palownia tomentosa*, Fam. Scrouphulariaceae). *Holz Roh Werkst*, **38**, 385-391 (1980).

Flynn, H. and C. Holder: Useful wood of the world. Forest Products Society. Madison, WI (2001).

Goker, Y., N. As, T. Akbulut and N. Ayrilmis: The technological properties and use of Carob wood. Review of the Faculty of Forestry, Vol. 49A. University of Istanbul, Istanbul (1999).

Guller, B. and N. Ay: Some mechanical properties of Alder [*Alnus glutinosa* subsps. *barbata* (C.A. Mey.) Yalt.] wood obtained from Artvin region. *Turk. J. Agric. For.*, **25**, 129-138 (2001).

Hernandez, E.R.: Influence of accessory substances, wood density and interlocked grain on the compressive properties of hardwoods. *Wood Sci. Technol.*, **41**, 249-265 (2007).

Kalaycioglu, H., I. Deniz and S. Hiziroglu: Some of the properties of particleboard made from paulownia. *J. Wood Sci.*, **51**, 410-414 (2005).

Kang, K.H., H. Huh, B.K. Kim and C.K. Lee: An antiviral furanoquinone from *Paulownia tomentosa* Steud. *Phytotherapy Res.*, **13**, 624-626. (1999).

Kollmann, F.F.P. and W.A. Cote: Principles of wood science and technology. I: Solid Wood. Springer-Verlag, Berlin-Heidelberg, Germany (1984).

Korkut, S. and B. Guller: Physical and mechanical properties of European Hophornbeam (Ostrya carpinifolia Scop.) wood. *Bioresource Technol.*, **99**, 4780-4785 (2008).

Liao, L., H. Mei, J. Li and Z. Li: Estimation and prediction on retention times of components from essential oil of *Paulownia tomentosa* flowers by molecular electronegativity-distance vector (MEDV). *J. of Molecular Structure*, *THEOCHEM*, **850**, 1-8 (2008).

Malkocoglu, A.: Dogu kayini (*Fagus orientalis* L.) odununun teknolojik özellikleri. Doktora Tezi, KTU, Orman Fakultesi, Trabzon (1994).

Ors, Y. and N. Ay: Physical properties of Alder [*Alnus glutinosa* subsps. *barbata* (C.A. Mey.) Yalt.] wood obtained from Rize-Çayeli region. *Turk. J. Agric. For.*, **23**, 803-808 (1999).

Ors, Y. and H. Keskin: Agac malzeme bilgisi. Atlas yayin dagitim. Ankara p. 183 (2001).

Ors, Y. and A. Senel: Thermal conductivity coefficients of wood and wood-based materials. *Turk. J. Agric. For.*, **23**, 239-246 (1999).

Pernestal, K., B. Jonsson and B. Larsson: A simple model for density of annual rings. *Wood Sci. Technol.*, **29**, 441-449 (1995).

Rai, A.K., S.P. Singh, C. Luxmi and G. Savita: Paulownia fortunei – A new ûber source for pulp, paper. *Indian Pulp Paper Tech. Assoc.*, **12**, 51-56 (2000).

Silvestre, A.J.D., D.V. Evtuguin, A.P.M. Sousa and A.M.S. Silva: Lignans from a hybrid Paulownia wood. *Biochem. Syst. Ecol.*, **33**, 1298-1302 (2005).

TS 642 ISO 554: Standard atmospheres for conditioning and/or testing; Specifications. Turkish Standard Institution, Ankara, Turkey (1997).

TS 2471: Wood - Determination of moisture content for physical and mechanical tests. Turkish Standard Institution, Ankara, Turkey (1976).

TS 2472: Wood - Determination of density for physical and mechanical tests. Turkish Standard Institution, Ankara, Turkey (1976).

TS 2474: Wood - Determination of ultimate strength in static bending. Turkish Standard Institution, Ankara, Turkey (1976).

TS 2478: Wood - Determination of modulus of elasticity in static bending. Turkish Standard Institution, Ankara, Turkey (1976).

TS 2479: Wood - Determination of static hardness. Turkish Standard Institution, Ankara, Turkey (1976).

TS 2595: Wood - Determination of ultimate stress in compression parallel to grain. Turkish Standard Institution, Ankara, Turkey (1977).

TS 4083: Wood - Determination of radial and tangential shrinkage. Turkish Standard Institution, Ankara, Turkey (1983).

TS 4084: Wood - Determination of radial and tangential swelling. Turkish Standard Institution, Ankara, Turkey (1983).

TS 4176: Wood - Sampling sample trees and long for determination of physical and mechanical properties of wood in homogeneous stands. Turkish Standard Institution, Ankara, Turkey (1984).

Ulu, F., S. Cetiner, N. Eren and S. Ayan: Result of the field stage in third year of species and provenances trials of Paulownia Sieb. and Zucc. in Eastern Black Sea region. Proceedings IUFRO Meeting management of fast growing plantations (*Ed.*: A. Diner *et al.*), DIV.4.04.06, 11th-13th September 2002, Izmit, Turkey. pp. 174-182 (2002).

Zhu, Z.H., C.J. Chao, X.Y. Lu and Y.G. Xiong: Paulownia in China: Cultivation and utilization. Singapore: Asian Network Biological Sciences and International Development Research Center of Canada, Canada (1986).